



**Queensland University of Technology**  
Brisbane Australia

This is the author's version of a work that was submitted/accepted for publication in the following source:

Martens, Wayde N., Frost, Ray L., Kloprogge, J. Theo, & Williams, Peter (2003) The basic copper arsenate minerals olivenite, cornubite, cornwallite, and clinoclase: An infrared emission and Raman spectroscopic study. *American Mineralogist*, 88(4), pp. 501-508.

This file was downloaded from: <http://eprints.qut.edu.au/21932/>

© Copyright 2003 Mineralogical Society of America

**Notice:** *Changes introduced as a result of publishing processes such as copy-editing and formatting may not be reflected in this document. For a definitive version of this work, please refer to the published source:*

# The basic copper arsenate minerals olivenite, cornubite, cornwallite and clinoclase: an infrared emission and Raman spectroscopic study

Ray L. Frost\*, Wayde N. Martens, J. Theo Kloprogge and Peter A. Williams\*

Centre for Instrumental and Developmental Chemistry, Queensland University of Technology, GPO Box 2434, Brisbane Queensland 4001, Australia.

\*School of Science, Food and Horticulture, University of Western Sydney, Locked Bag 1797, Penrith South DC NSW 1797, Australia

## ABSTRACT

Molecular structures of the basic copper arsenate minerals olivenite, cornubite, cornwallite and clinoclase have been studied using a combination of infrared emission spectroscopy and Raman spectroscopy. Infrared emission spectra of the basic copper arsenates have been obtained over the temperature range 100 to 1000°C. IR emission spectra of the four minerals are different, in line with differences in crystal structure and composition. Raman spectra are similar, particularly in the OH-stretching region, but characteristic differences in the deformation regions are observed. Differences are also observed in the arsenate stretching and bending regions. IR emission studies show that the minerals are completely dehydroxylated by 550°C.


**Key Words-** copper, arsenate, olivenite, cornubite, cornwallite, clinoclase, infrared emission, Raman spectroscopy

## INTRODUCTION

A number of dark emerald-green copper arsenate minerals containing no water of crystallization are known from the oxidized zones of base metal deposits (Anthony et al. 2000). These include olivenite [ $\text{Cu}_2\text{AsO}_4\text{OH}$ ], the most common member of the group. Related species are the dimorphous pairs cornwallite and cornubite [ $\text{Cu}_5(\text{AsO}_4)_2(\text{OH})_4$ ] and clinoclase and gilmarite [ $\text{Cu}_3\text{AsO}_4(\text{OH})_3$ ]. Gilmarite is extremely rare, having been reported from a single French locality (Sarp and Xerný 1999). Olivenite is monoclinic (pseudo-orthorhombic), space group  $P2_1/n$  (Berry 1951; Burns and Hawthorne 1995; Toman 1977). Cornwallite (monoclinic, space group  $P2_1/c$ ; Arit and Armbruster 1999) is isomorphous with pseudomalachite [ $\text{Cu}_5(\text{PO}_4)_2(\text{OH})_4$ ] and is more common than its triclinic (space group  $P\bar{1}$ ) dimorph cornubite (Tillmans et al 1985). The rare species clinoclase has also been structurally characterized; it is monoclinic, space group  $P2_1/a$  (Eby and Hawthorne 1990; Ghose et al. 1965). A summary of crystallographic properties of the basic copper arsenates relevant to this study is given in Table 1.

---

\* Author for correspondence (r.frost@qut.edu.au)

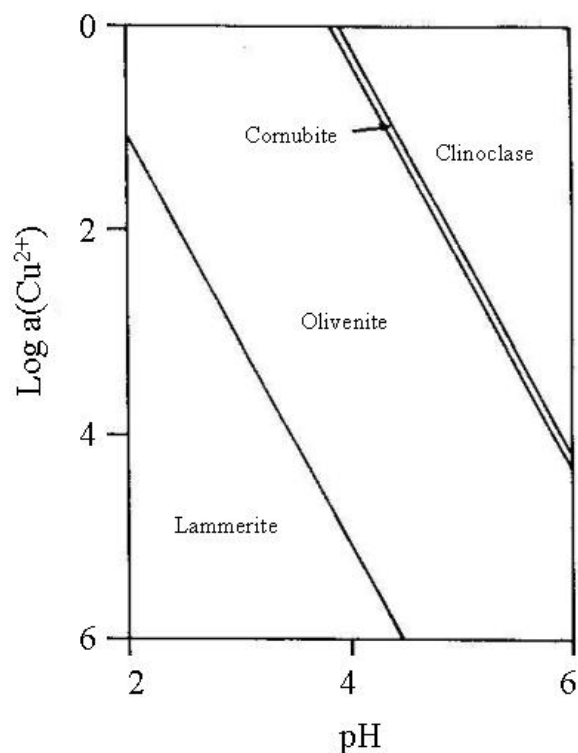

**Figure 1 Phase relationship of some of the basic copper arsenate minerals (after Williams, 1990)**

Relative stabilities of some of the anhydrous basic copper arsenates are shown in Figure 1, based on the experimentally derived data of Magalhães et al. (1988). The more basic stoichiometries occupy fields at higher pH as expected. Cornwallite (or cornubite) is the stable phase under chemical conditions intermediate to those that serve to stabilize olivenite and clinoclase and paragenetic relationships between the phases have been explored (Williams 1990). Normal anhydrous copper(II) arsenate is known as the naturally occurring species lammerite [ $\text{Cu}_3(\text{AsO}_4)_2$ ], but it is very rare (Anthony et al. 2000). Similarly, yvonite [ $\text{CuHAsO}_4 \cdot 2\text{H}_2\text{O}$ ] is known from only one locality (Sarp and Xerný 1998). Thus this study has concentrated on the more common anhydrous minerals of the group. Their chemical similarities suggest that they would have similar vibrational spectra, but structural differences indicate that these should be readily distinguishable.

Whilst the infrared spectra of many minerals have been forthcoming, few comprehensive studies of related minerals such as the basic copper arsenates have been undertaken (Braithwaite 1983; Gevork'yan and Povarennykh 1975; Paques-Ledent and Tarte 1974). Structural investigations of some arsenates and in terms of the nature of hydrogen bonds present have been forthcoming, but the minerals selected in this study were fundamentally unrelated. It was found that the hydroxyl unit was coordinated directly to the metal ion and formed hydrogen bonds to the arsenate anion (Sumin De Portilla 1974). Cation substitution and ordering in the olivenite-adamite [ $\text{Zn}_2\text{AsO}_4\text{OH}$ ] series has been investigated by IR methods (Chisholm 1985), but similar studies for related species are lacking. In addition, very

few Raman studies of these kinds of species have been undertaken (Griffith 1969a,b, 1970). As part of a comprehensive study of the molecular structure of secondary minerals containing oxyanions using IR and Raman spectroscopy, we report the vibrational properties of olivenite, cornubite, cornwallite and clinoclase, together with an infrared emission study of their dehydration.

## EXPERIMENTAL

### Minerals

The sample of cornubite from the Daly mine, Flinders Ranges, South Australia was obtained from the collections of the Mineralogy Section, Museum Victoria, Melbourne, Victoria, Australia (specimen M37793). Cornwallite and olivenite from the Penberthy Croft mine, St Hilary, Cornwall, UK, were supplied by Mr John Betterton. Samples of olivenite and clinoclase from the Tin Stope, Majuba Hill mine, Utah, USA, were purchased from the Mineralogical Research Company. All were checked for purity by powder by X-ray diffraction and by SEM and microprobe methods. Negligible amounts of phosphorus or transition metals other than copper were found in the samples used for the spectroscopic study.

### Infrared emission spectroscopy

FTIR emission spectroscopy was carried out on a Nicolet spectrometer equipped with a TGS detector, modified by replacing the IR source with an emission cell. A description of the cell and principles of the emission experiment have been published elsewhere (Frost et al. 1999; Frost and Vassallo 1996; Kloprogge and Frost 2000). Approximately 0.2 mg of each basic copper arsenate was spread as a thin layer (approximately 0.2 microns thick) on a 6 mm diameter platinum surface and held in an inert atmosphere within a nitrogen-purged cell during heating.

In the normal course of events, three sets of spectra are obtained. First, black body radiation over the temperature range selected at the various temperatures is obtained. Secondly, the platinum plate radiation is obtained at the same temperatures and thirdly spectra from the platinum plate covered with the sample is measured. Normally only one set of black body and platinum radiation is required. The emittance spectrum ( $E$ ) at a particular temperature was calculated by subtraction of the single beam spectrum of the platinum backplate from that of the platinum ( $Pt$ ) + sample ( $S$ ), and the result ratioed to the single beam spectrum of an approximate black body (graphite,  $C$ ). The following equation was used to calculate the emission spectra.

$$E = -0.5 \log \{(Pt-S)/(Pt-C)\}$$

This manipulation was carried out after all spectroscopic data had been collected. Emission spectra were collected at intervals of 50°C over the range 200 - 750°C. The time between scans (while the temperature was raised to the next hold point) was approximately 100 seconds. It was considered that this was sufficient time for the heating block and the powdered sample to reach temperature equilibrium. Spectra were acquired by co-addition of 64 scans for the whole temperature range

(approximate scan time 45 seconds), with a nominal resolution of  $4\text{ cm}^{-1}$ . Good quality spectra can be obtained providing the sample thickness is not too large. If too large a sample is used, spectra become difficult to interpret because of the presence of combination and overtone bands. Spectroscopic manipulation such as baseline adjustment, smoothing and normalisation was performed using the GRAMS® software package (Galactic Industries Corporation, Salem, NH, USA).

### Raman Spectroscopy

Crystals of the minerals were placed and orientated on a polished metal surface on the stage of an Olympus BHSM microscope, which is equipped with 10x and 50x objectives. The microscope is part of a Renishaw 1000 Raman microscope system, which also includes a monochromator, a filter system and a Charge Coupled Device (CCD). Raman spectra were excited by a Spectra-Physics model 127 He-Ne laser (633 nm) at a resolution of  $2\text{ cm}^{-1}$  in the range between 100 and  $4000\text{ cm}^{-1}$ . Repeated acquisitions using the highest magnification were accumulated to improve the signal-to-noise ratio. Spectra were calibrated using the  $520.5\text{ cm}^{-1}$  line of a silicon wafer. Spectra at liquid nitrogen temperature were obtained using a Linkam thermal stage (Scientific Instruments Ltd, Waterfield, Surrey, England).

Spectroscopic manipulation such as baseline adjustment, smoothing and normalisation were performed as described above. Band component analysis was undertaken using the Jandel 'Peakfit' software package, which enabled the type of fitting function to be selected and allowed specific parameters to be fixed or varied accordingly. Band fitting was done using a Gauss-Lorentz cross-product function with the minimum number of component bands used for the fitting process. The Gauss-Lorentz ratio was maintained at values greater than 0.7 and fitting was undertaken until reproducible results were obtained with squared correlations ( $r^2$ ) greater than 0.995.

## RESULTS AND DISCUSSION

Assignment of spectra of the tetrahedral anions in aqueous solutions is comparatively simple. The symmetric stretching vibration of the arsenate anion ( $\nu_1$ ) is observed at  $810\text{ cm}^{-1}$  and coincides with the position of the asymmetric stretching mode ( $\nu_3$ ). The symmetric bending mode ( $\nu_2$ ) is observed at  $342\text{ cm}^{-1}$  and the out-of-plane bending mode ( $\nu_4$ ) is observed at  $398\text{ cm}^{-1}$ . Of all tetrahedral oxyanion spectra, the positions of the arsenate vibrations occur at lower wavenumbers than is the case with most other naturally-occurring oxyanions. Farmer (1974) lists a number of spectra of arsenates including those of the basic copper arsenates olivenite and the related hydrated phase euchroite [ $\text{Cu}_2\text{AsO}_4\text{OH}\cdot 3\text{H}_2\text{O}$ ]. In the crystalline state, degeneracy is lifted and this allows splitting of the bands according to factor group analysis. Thus  $\nu_1$  and  $\nu_3$  bands of olivenite and euchroite were observed at 860, 828,  $790\text{ cm}^{-1}$  and 830 and  $770\text{ cm}^{-1}$ , respectively. Bending modes were found at 493 and  $452\text{ cm}^{-1}$  for olivenite and at 475 and  $410\text{ cm}^{-1}$  for euchroite. No  $\nu_2$  bands were shown. This is no doubt related to the fact the bands are found below  $400\text{ cm}^{-1}$ , which makes their measurement by infrared spectroscopy less appealing. Two OH stretching vibrations were observed at 3580 and  $3440\text{ cm}^{-1}$  for olivenite. A number of bands were listed which were unassigned.

## Infrared emission spectroscopy of the hydroxyl stretching vibrations

The infrared emission spectra of the hydroxyl stretching region of olivenite, cornubite, cornwallite and clinoclase are shown in Figures 2-5, respectively. IE spectra of olivenite shows three curve resolved hydroxyl stretches at 3553, 3447 and 3346  $\text{cm}^{-1}$  (at 150°C). Farmer (1974) reported two bands at 3580 and 3440  $\text{cm}^{-1}$ . The additional band reported here is a curve resolved component. These bands are in reasonable agreement with the IES data reported here. Raman spectra of the hydroxyl-stretching region of the four basic copper arsenate minerals are shown in Figure 6 and reveal the presence of two hydroxyl stretching vibrations at 3464 and 3437  $\text{cm}^{-1}$ . In the structure of olivenite there is one crystallographically-independent hydroxyl group (Burns and Hawthorne 1995; Toman 1977) and this suggests that one infrared emission band should be observed. However, there are three emission and two Raman stretching modes. If the proton on the hydroxyl unit were delocalised such that it could attach to the arsenate ion then AsOH moieties could provide the additional hydroxyl vibrations. The unit cell contains one crystallographically-independent arsenic atom bonded to four independent oxygen atoms. Hence the four AsOH units would not be identical and the spectrum of the hydroxyl vibrations would not be degenerate. The intensity of the higher wavenumber band observed at 3553  $\text{cm}^{-1}$  is lost before the other two hydroxyl-stretching bands and that at 3346  $\text{cm}^{-1}$  by 450°C. Variation of intensity-temperature plots in the 450 to 600°C region shows the temperature range over which dehydroxylation takes place. The positions of the hydroxyl stretching bands shift to higher wavenumbers with increasing temperature. This reflects a weakening of the bonding of the OH unit.

Three curve-resolved hydroxyl-stretching IES bands are observed for cornubite at 3535, 3416 and 3349  $\text{cm}^{-1}$  (100°C spectrum). Two additional low intensity bands are observed at 3329 and 3152  $\text{cm}^{-1}$ . Three bands are observed even in the 300°C spectrum. The two hydroxyl stretching bands at 3416 and 3349  $\text{cm}^{-1}$  are not observed at 400°C. The infrared spectrum of cornubite has not been previously published. Raman spectra show two bands at 3324 and 3042  $\text{cm}^{-1}$  (Frost et al. 2002). Cornubite contains two crystallographically independent OH units. Thus two hydroxyl stretching vibrations should be observed. However we observe three bands in the IES spectra. The two lower wavenumber vibrations observed at 3416 and 3349  $\text{cm}^{-1}$  could be attributed to these independent OH units. The higher wavenumber band at 3535  $\text{cm}^{-1}$  may be assigned to an AsOH unit if the protons are delocalised.

The data show that the intensities of the hydroxyl bands diminish at different rates. Importantly, IES data provide information on the temperature of dehydroxylation of the cornubite, such information being complementary to thermoanalytical techniques. However where rare minerals are involved less than 0.2 mg of sample is required for the IES technique as opposed to the thermoanalytical techniques where significantly more sample is required. Data for cornubite suggest that some intensity remains in the 3565  $\text{cm}^{-1}$  band up to 700°C. One possible explanation of the differences in the band positions between the Raman and infrared data rests with the symmetry of the molecule. The Raman technique measures the symmetric stretching modes whereas the infrared technique determines the antisymmetric stretching vibrations.

IES spectra of cornwallite show bands at 3526, 3417 and 3352  $\text{cm}^{-1}$  with two additional low intensity bands at 3291 and 3132  $\text{cm}^{-1}$ . Cornubite and cornwallite are dimorphs and hence might be expected to have similar spectra in the hydroxyl stretching region. The spectra in Figures 3 and 4 show similarity in profiles, but bands for cornwallite are observed at lower wavenumbers. Cornwallite Raman spectra show two bands at 3411 and 3350  $\text{cm}^{-1}$  (Frost et al. 2002), in excellent agreement with the latter two IES bands. Cornwallite contains two crystallographically independent OH units, while three bands are observed in the IES spectra. The two lower wavenumber vibrations at 3417 and 3352  $\text{cm}^{-1}$  could be attributed to the independent OH units and the higher wavenumber band at 3526  $\text{cm}^{-1}$  to an AsOH moiety. As for cornubite the intensity approaches zero by 400°C and cornwallite is completely dehydroxylated by 400°C.

Clinoclase is dimorphous with gilmarite and contains three crystallographically independent OH units. The IES spectrum of gilmarite was not obtained, as no specimen was available. For clinoclase, two prominent IES bands are observed at 3354 and 3346  $\text{cm}^{-1}$  with component bands also observed at 3558 and 3349  $\text{cm}^{-1}$ . Another band is observed at 3115  $\text{cm}^{-1}$  but is of very low intensity. It is proposed that the bands at 3354, 3346 and 3349  $\text{cm}^{-1}$  bands are assignable to the three independent OH units. The higher wavenumber band at 3558  $\text{cm}^{-1}$  is ascribed to an AsOH unit. Raman spectra of clinoclase display two bands at 3559 and 3339  $\text{cm}^{-1}$ . A possible interpretation of the vibrational data of clinoclase for the hydroxyl stretching region is that the two Raman bands are attributable to the symmetric stretching vibrations, which are observed in the IES spectra but are weak. The intense bands in the IES spectra are attributable to antisymmetric stretching vibrations. As for the other basic copper arsenates, intensity approaches zero by 400°C and the intensity of each band appears to decrease at the same rates.

### **Infrared emission spectroscopy of the hydroxyl deformation vibrations**

Infrared spectra of the 650 to 1850  $\text{cm}^{-1}$  region of the four basic copper arsenates are shown in Figures 7-10 respectively. This region shows several features: bands in the region between 1200 and 1850 (overtone bands), features between 950 to 990  $\text{cm}^{-1}$  in the region assignable to hydroxyl deformation modes and absorption in the 650 to 900  $\text{cm}^{-1}$  region where the AsO symmetric and antisymmetric stretching modes are located. For olivenite, two low intensity bands are observed at 987 and 943  $\text{cm}^{-1}$ . The intensity of these bands approaches zero by 350°C. These bands are assigned to hydroxyl deformation modes. Observation of two hydroxyl deformation modes is in harmony with the observation of two major hydroxyl stretching vibrations. In Raman spectra of olivenite a single band at 957  $\text{cm}^{-1}$  was observed (Figure 11); a second band at 1033  $\text{cm}^{-1}$  may also be an hydroxyl deformation mode although the position is high for this type of vibration.

In IES spectra of cornubite, two low intensity bands are observed at 983 and 970  $\text{cm}^{-1}$ ; these disappear by 300°C. Two Raman bands were observed for cornubite at 962 and 1051  $\text{cm}^{-1}$ , in line with its crystal structure, and these are assigned to hydroxyl deformation modes of the OH units. For cornwallite two bands are found at 989 and 958  $\text{cm}^{-1}$ , but low intensity Raman bands were observed at 962, 997, 1035 and 1093  $\text{cm}^{-1}$ . The first two are in harmony with the two IES bands and diminish in

intensity with increasing temperature and disappear at 400°C. The bands are attributed to hydroxyl deformation modes of OH units bonded to Cu atoms. For clinoclase, more intense bands are observed at 985 cm<sup>-1</sup>, 1078 and 1114 cm<sup>-1</sup>, and which decrease in intensity with increasing temperature. In the Raman spectrum, a single band at 985 cm<sup>-1</sup> is observed and which is in an identical position to the IES band. These three bands are attributed to hydroxyl deformation modes of clinoclase and fit well with the observation of three independent OH units in the unit cell.

### **Arsenate vibrational modes**

IES spectra of the low wavenumber region of the AsO<sub>4</sub> units of the four basic copper arsenates are shown in Figures 7 to 10. Whilst infrared emission spectroscopy is excellent for the determination of the hydroxyl-stretching region, measurement of the lower wavenumber region suffers from overlap of the bands and also from the observation of combination bands. The latter are observed in the region between 1300 and 2000 cm<sup>-1</sup> and result from the combination of bands in the 650 to 1000 cm<sup>-1</sup> region. Raman spectra of the 700 to 1200 cm<sup>-1</sup> region of the four basic copper arsenate minerals is shown in Figure 11. The advantage of Raman spectroscopy in the AsO stretching region is that the spectra are less complex and Raman spectra are therefore most useful for determining vibrational modes of the arsenate ion.

Raman spectra of olivenite show two bands at 853 and 819 cm<sup>-1</sup> assigned to in-phase and out-of-phase AsO stretching. A band is observed in the IES spectrum at 853 cm<sup>-1</sup> and a second intense band at 808 cm<sup>-1</sup>. These values are in harmony with the Raman measurements. Crystallographically, olivenite contains one independent arsenate ion with four independent oxygen atoms. Providing there is no loss of degeneracy one would expect only one symmetric and one antisymmetric stretching vibration. An IES band is observed at 779 cm<sup>-1</sup> with significant intensity is attributed to the antisymmetric stretching vibration. The spectra in Figure 6 show a low intensity band at 693 cm<sup>-1</sup>, the intensity of which approaches zero during heating, and thus fits the pattern of a hydroxyl deformation vibration. One possibility is that the band is due to the deformation of the AsOH unit formed from the delocalisation of the hydroxyl proton. If the OH unit is weakly bonded, as could be expected for a delocalised proton, the hydroxyl stretching band would occur at the upper end of the OH stretching vibrations and the OH deformation would occur at the lower wavenumbers.

For cornubite, two Raman bands are observed at 815 and 780 cm<sup>-1</sup> and are assigned to the antisymmetric and symmetric stretching modes. Two bands are observed in the IES spectra at 819 and 788 cm<sup>-1</sup>, in harmony with the Raman bands. These may correspond with the two independent OH units in the lattice. Two bands in the spectra are observed at 819 and 759 cm<sup>-1</sup>, both of which appear to be hydroxyl deformation modes since they are lost by 300°C. Raman bands are observed for cornwallite at 877, 859, 806 and 763 cm<sup>-1</sup> and IES bands at 829, 816, 796 and 779 cm<sup>-1</sup>. It appears that two sets of symmetric and antisymmetric stretching modes are observed. Thus both the Raman and infrared spectra of cornwallite are quite different to those of cornubite, probably because of variable coupling phenomena in the different space groups. A low intensity band at 695 cm<sup>-1</sup>, attributed to the AsOH unit, is lost by 300°C. Raman spectra of clinoclase show bands at 850, 832 and 783 cm<sup>-1</sup> and IES bands at 861, 831, 784 cm<sup>-1</sup> in harmony with the Raman data.

## CONCLUSIONS

The application of infrared emission and Raman spectroscopy techniques has enabled the structure of the four phase-related basic copper arsenates to be probed. A comparison is made between the molecular structures of these four related minerals. Infrared emission spectroscopy was used to explore the dehydroxylation of the minerals and confirms the band positions of the hydroxyl deformation modes. The loss of intensity of the hydroxyl deformation modes paralleled that of the hydroxyl stretching vibrations and approached zero at the dehydroxylation temperature. Structural changes were also observed through variation in the band centres and the peak widths of selected bands. Importantly the IES technique enables the study of the dehydration and dehydroxylation of rare minerals as less than 0.1 mg may be used.

## ACKNOWLEDGMENTS

The financial and infra-structure support of the Queensland University of Technology Centre for Instrumental and Developmental Chemistry is gratefully acknowledged. The Australian research Council (ARC) is thanked for funding. We would like to thank Mr Dermot Henry Museum Victoria and Mr John Betterton for their help in obtaining some of the specimens used in this study.

## REFERENCES CITED

- Anthony J.W., Bideaux, R., Bladh, K.W. and Nichols, M.C. (2000) Handbook of Mineralogy Volume IV arsenates, phosphates and vanadates. Mineral Data Publishing, Tuscon, Arizona, USA, 2000.
- Arit, T. and Armbruster, T. (1999) Single-crystal X-ray structure refinement of cornwallite,  $\text{Cu}_5(\text{AsO}_4)_2(\text{OH})_4$ : a comparison with its polymorph cornubite and the  $\text{PO}_4$ -analogue pseudomalachite. *Neues Jahrbuch für Mineralogie, Monatshefte*, 468-480.
- Berry, L.G. (1951) Observations of conichalite, cornwallite, euchroite, liroconite and olivenite. *American Mineralogist*, 36, 484-503.
- Braithwaite, R.S.W. (1983) Infrared spectroscopic analysis of the olivenite-adamite series, and of phosphate substitution in olivenite. *Mineralogical Magazine*, 47, 51-7.
- Burns, P.C. and Hawthorne, F.C. (1995) Rietveld refinement of the crystal structure of olivenite: a twinned monoclinic structure. *Canadian Mineralogist*, 33, 885-8.
- Chisholm, J.E. (1985) Cation segregation and the O-H stretching vibration of the olivenite-adamite series. *Physics and Chemistry of Minerals*, 12, 185-90.
- Eby, R.K. and Hawthorne, F.C. (1990) Clinoclase and the geometry of [5]-coordinate copper<sup>2+</sup> in minerals. *Acta Crystallographica*, C46, 2291-4.
- Farmer, V.C. (1974) *Mineralogical Society Monograph 4: The Infrared Spectra of Minerals*. 539 pp.
- Frost R.L., Martens W.N. and Williams P.A. (2002) Raman spectroscopy of the phase related basic copper arsenate minerals: olivenite, cornwallite, cornubite and clinoclase. *Journal of Raman Spectroscopy*, (2002) submitted.

- Frost, R.L., Kloprogge, J.T., Russell, S.C. and Szetu, J. (1999) Dehydroxylation and the vibrational spectroscopy of aluminum (oxo)hydroxides using infrared emission spectroscopy. Part III: diaspore. *Applied Spectroscopy*, 53, 829-835.
- Frost, R.L. and Vassallo, A.M. (1996) The dehydroxylation of the kaolinite clay minerals using infrared emission spectroscopy. *Clays and Clay Minerals*, 44, 635-651.
- Gevork'yan, S.V. and Povarennykh, A.S. (1975) The IR spectra of some hydroxyl-containing copper and zinc phosphates and arsenates. *Konst. Svoistva Miner.*, 9, 73-81.
- Ghose, S., Fehlmann, M. and Sundaralingam, M. (1965) The crystal structure of clinoclase,  $\text{Cu}_3\text{AsO}_4(\text{OH})_3$ . *Acta Crystallographica*, 18, 777-87.
- Griffith, W.P. (1969a) Raman spectroscopy of minerals. *Nature (London)*, 224, 264-6.
- Griffith, W.P. (1969b) Raman studies on rock-forming minerals. I. Orthosilicates and cyclosilicates. *Journal of the Chemical Society A*, 1372-7.
- Griffith, W.P. (1970) Raman studies on rock-forming minerals. II. Minerals containing  $\text{MO}_3$ ,  $\text{MO}_4$ , and  $\text{MO}_6$  groups. *Journal of the Chemical Society A*, 286-91.
- Kloprogge, J.T. and Frost, R.L. (2000) Study of the thermal behaviour of rectorite by in-situ infrared emission spectroscopy. *Neues Jahrbuch für Mineralogie, Monatshefte*, 145-157.
- Magalhães, M.C.F., Pedrosa de Jesus, J.D. and Williams, P.A. (1988) The chemistry of formation of some secondary arsenate minerals of Cu(II), Zn(II) and Pb(II). *Mineralogical Magazine*, 52, 679-90.
- Paques-Ledent, M.T. and Tarte, P. (1974) Vibrational studies of olivine-type compounds. II. Orthophosphates, -arsenates and -vanadates  $\text{A}(\text{I})\text{B}(\text{II})\text{X}(\text{V})\text{O}_4$ . *Spectrochimica Acta*, 30A, 673-89.
- Sarp, H. and Xerný, R. (1998) Description and crystal structure of yvonite,  $\text{Cu}(\text{AsO}_3\text{OH})_2 \cdot 2\text{H}_2\text{O}$  *American Mineralogist*, 83, 383-9.
- Sarp, H. and Xerný, R. (1999) Gilmarite,  $\text{Cu}_3(\text{AsO}_4)(\text{OH})_3$ , a new mineral its description and crystal structure. *European Journal of Mineralogy*, 11, 549-555.
- Sumin De Portilla, V.I. (1974) Infrared spectroscopic investigation of the structure of some natural arsenates and the nature of hydrogen-bonds in their structures. *Canadian Mineralogist*, 12, 262-8.
- Tillmanns, E., Hofmeister, W. and Petitjean, K. (1985) Cornubite,  $\text{Cu}_5\text{AsO}_4)_2(\text{OH})_4$ , first occurrence of single crystals, mineralogical description and crystal structure. *Bulletin of the Geological Society of Finland*, 57, 119-127.
- Toman, K. (1977) The symmetry and crystal structure of olivenite. *Acta Crystallographica*, B33, 2628-2631.
- Williams, P.A. (1990) *Oxide Zone Geochemistry*. Ellis Horwood Ltd, Chichester, West Sussex, England,.

<b>Olivinite</b> (Burns and Hawthorne 1995; Toman 1977)	<b>Cornubite</b> (Tillmanns et al. 1985)	<b>Cornwallite</b> (Arlt and Armbruster 1999)	<b>Clinoclase</b> (Eby and Hawthorne 1990)	<b>Gilmarite</b> (Sarp and Cerny 1999)
Monoclinic, $P2_1/n$	Triclinic, $P\bar{1}$	Monoclinic, $P2_1/c$	Monoclinic, $P2_1/a$	Triclinic, $P1$
Forms a series with adamite, $Zn_2AsO_4OH$	Dimorphous with cornwallite	Dimorphous with cornubite.	Dimorphous with gilmarite.	Dimorphous with clinoclase.
Forms a series libethenite, $Cu_2PO_4(OH)$ .	Comparable with the corresponding phosphate trimorphs pseudomalachite, ludjibaite and reichenbachite.	Isomorphous with pseudomalachite.	Comparable with cornetite, $Cu_3PO_4(OH)_3$ is orthorhombic.	Comparable with cornetite, $Cu_3PO_4(OH)_3$ , orthorhombic, $Pbca$ .
<i>Pseudo</i> -orthorhombic with one crystallographically independent arsenate ion containing four independent oxygen atoms.	The cornubite crystal structure contains one As atom in the asymmetric unit (total of 2 in the cell) The arsenic is bonded to 4 crystallographically independent oxygen atoms.	Cornwallite, although crystallizing in a different space group, has the same number of independent As and arsenate O atoms and OH ions as does cornubite.	There are three crystallographically independent OH ions in the unit cell, with a total of twelve.	With the space group constraints, all atoms in the unit cell (one formula unit) are crystallographically independent.
One independent OH group in the unit cell.	There are two crystallographically independent OH ions.	There are two crystallographically independent OH ions.	There is one As atom (total 4) bonded to four independent oxygen atoms.	

**Table 1 Summary of the crystallographic properties of the basic copper arsenates.**

## List of Figures

- Figure 1 Phase relationship of some of the basic copper arsenate minerals (after Williams, 1990)
- Figure 2 Infrared emission spectra of the hydroxyl-stretching region of olivenite from 150 to 600°C at 50°C intervals.
- Figure 3 Infrared emission spectra of the hydroxyl-stretching region of cornubite from 150 to 600°C at 50°C intervals.
- Figure 4 Infrared emission spectra of the hydroxyl-stretching region of cornwallite from 150 to 600°C at 50°C intervals.
- Figure 5 Infrared emission spectra of the hydroxyl-stretching region of clinoclase from 150 to 600°C at 50°C intervals.
- Figure 6 Raman spectra of the hydroxyl-stretching region of (a) olivenite (b) cornubite (c) cornwallite (d) clinoclase
- Figure 7 Infrared emission spectra of the low wavenumber region of olivenite from 150 to 600°C at 50°C intervals.
- Figure 8 Infrared emission spectra of the low wavenumber region of cornubite from 150 to 600°C at 50°C intervals.
- Figure 9 Infrared emission spectra of the low wavenumber region of cornwallite from 150 to 600°C at 50°C intervals.
- Figure 10 Infrared emission spectra of the low wavenumber region of clinoclase from 150 to 600°C at 50°C intervals.
- Figure 11 Raman spectra of the 700 to 1200  $\text{cm}^{-1}$  region of (a) olivenite (b) cornubite (c) cornwallite (d) clinoclase

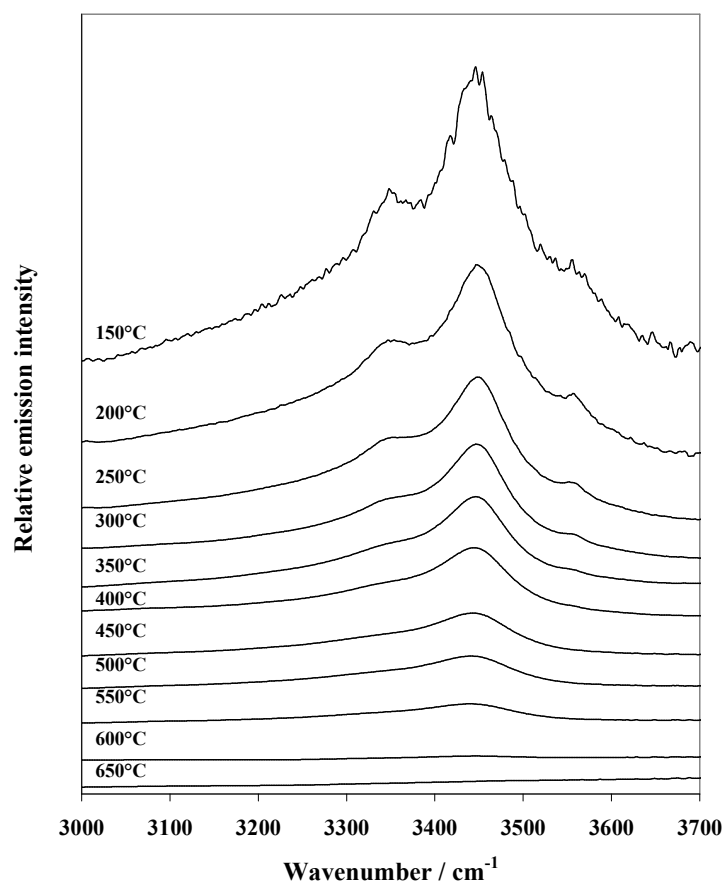


Figure 2

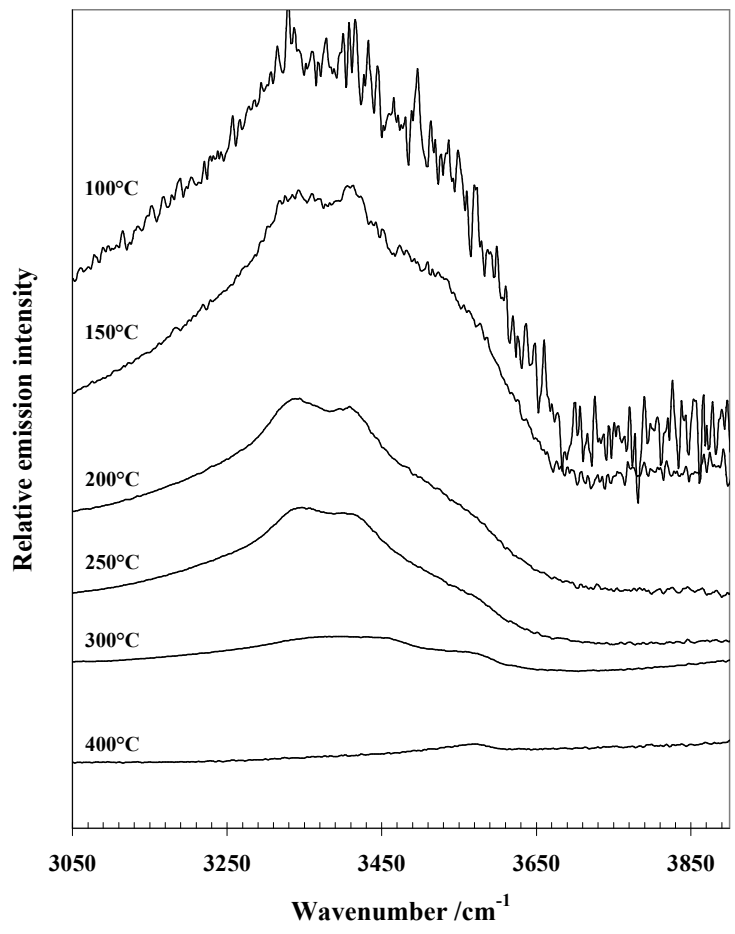


Figure 3

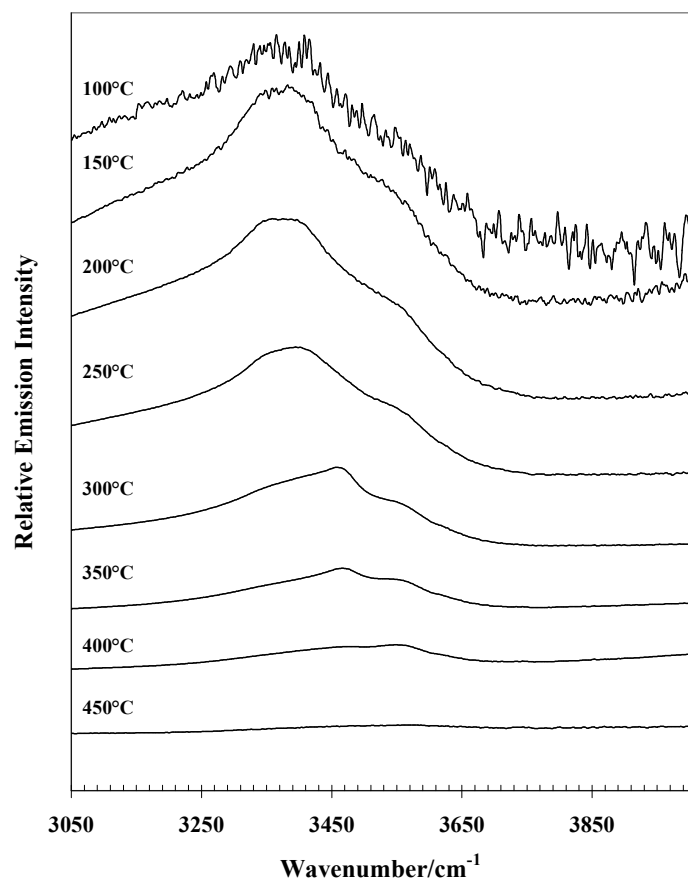


Figure 4

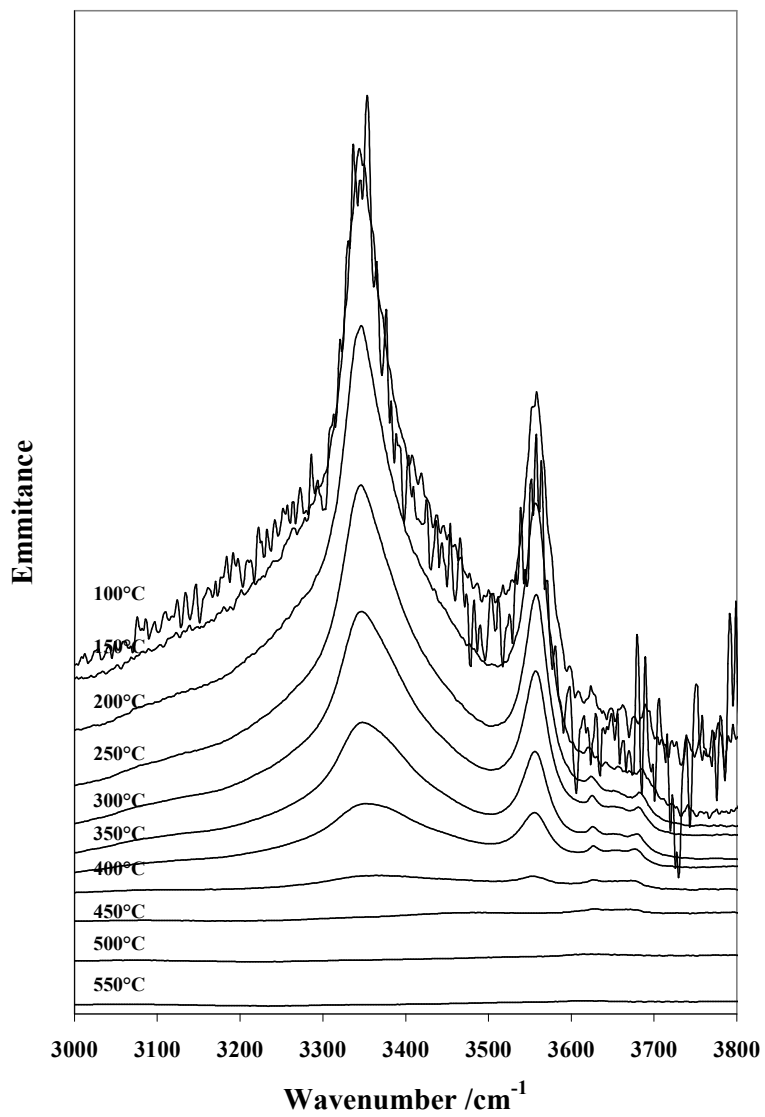


Figure 5

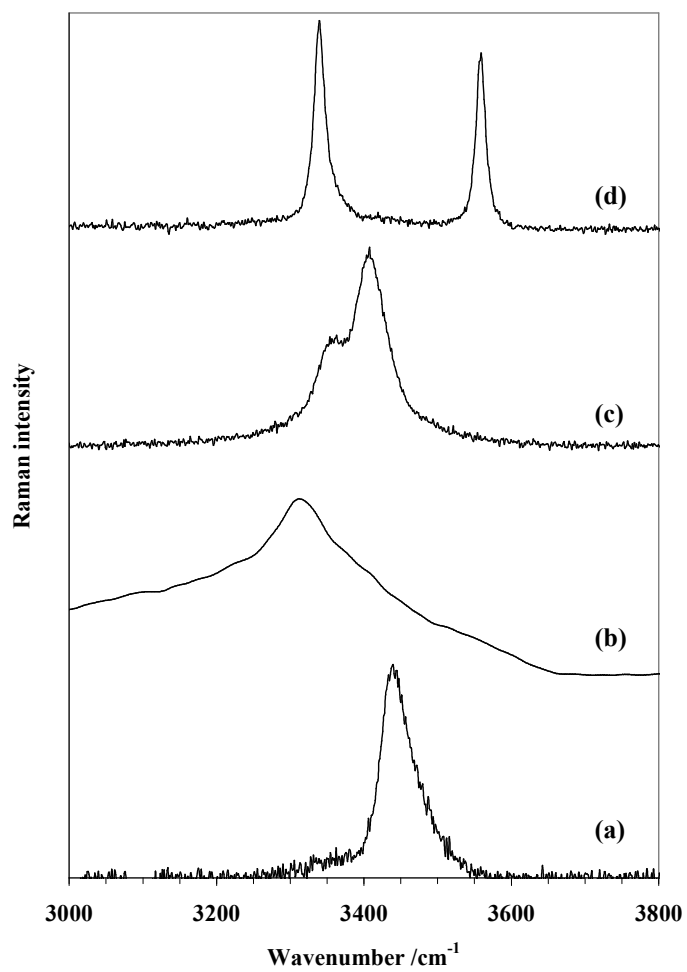


Figure 6

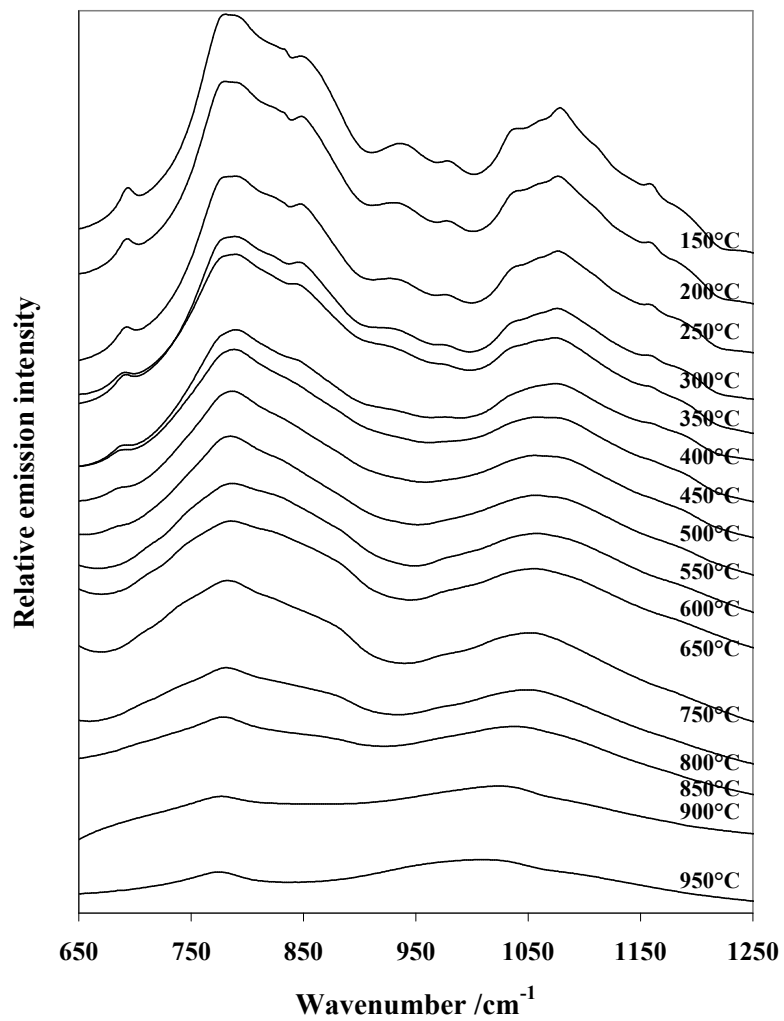


Figure 7

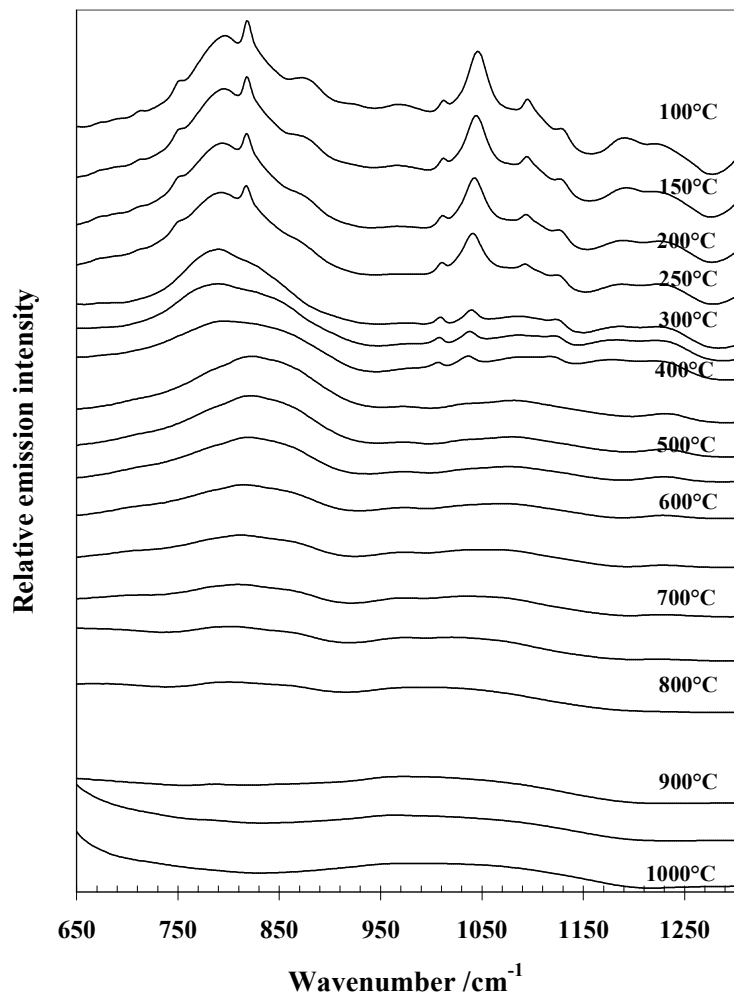


Figure 8

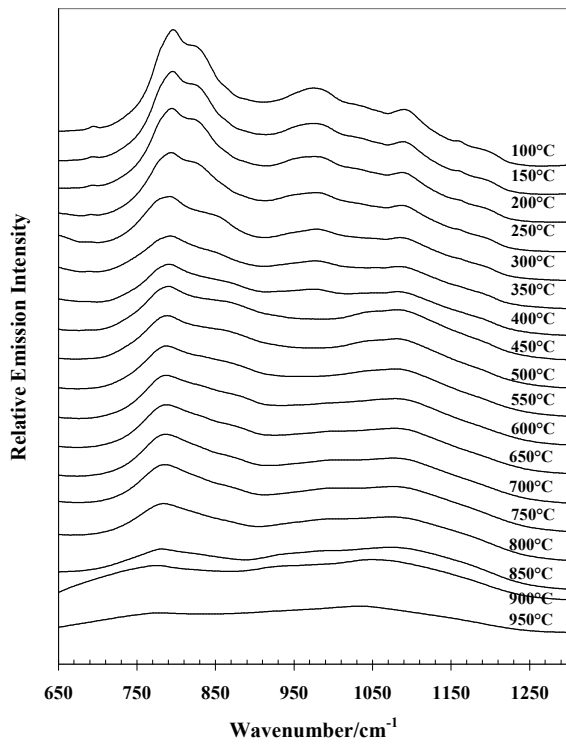


Figure 9

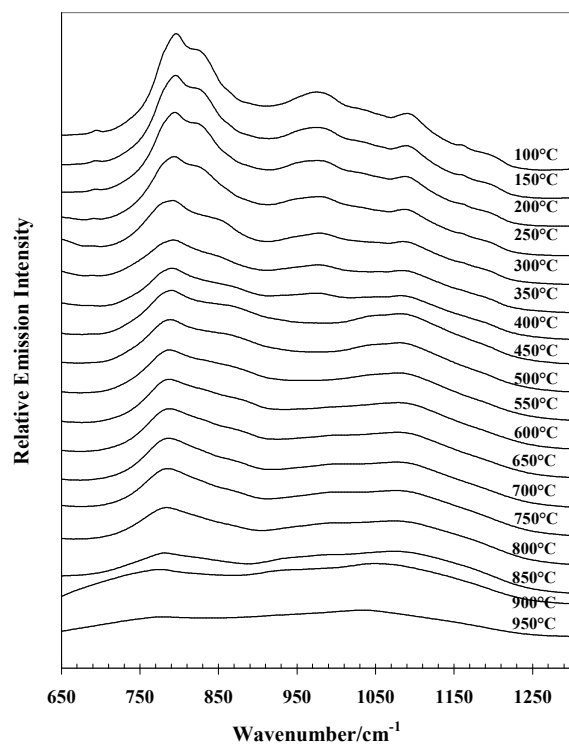


Figure 10

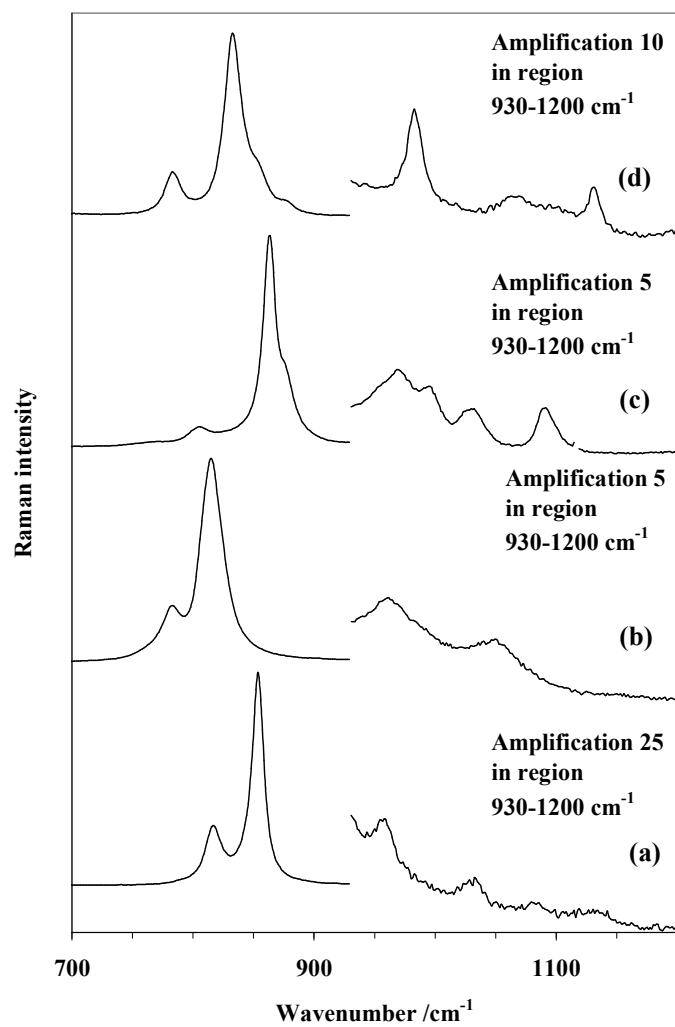


Figure 11

## **List of Tables**

**Table 1 Summary of the crystallographic properties of the basic copper arsenates**